KLEINFELDER
EXPECT MORE®
AN EMPLOYEE OWNED COMPANY

3601 Manor Road / Austin, Texas
512-926-6650 / fax 512-926-3312
www.kleinfelder.com

TO: A.R.M. (Austin Reclaimed Materials)
Attn.: Mr. Troy Carter
P.O. Box 27935
Austin, Texas 78755

PROJECT: 2006 Annual A.R.M.

PROJECT NO.: 66166
DATE: 2-9-07
CONTROL NO.: 020613 B

Test Method:	**ASTM D 698-00**
Sample Number:	S-16481
Sample Location:	Naumann Pit
Sampled By:	Client
Date Sampled:	2-6-07
Test Method:	**ASTM D 4318-00** **ASTM D 2487-00** **ASTM D 1140-00**
Material Description:	"C" Loam (Brown Sandy Lean Clay)
Liquid Limit:	27
Plastic Limit:	17
Plasticity Index:	10
Retained on 3":	0
Retained on #4:	0
Retained on #40:	0.6
Retained on #200:	42.2
Group Symbol:	CL
Preparation Method:	Moist
Rammer:	Mechanical
Compaction Method:	A
Oversize Sieve :	#4
% By Weight Oversize:	NA
Bulk Specific Gravity:	NA

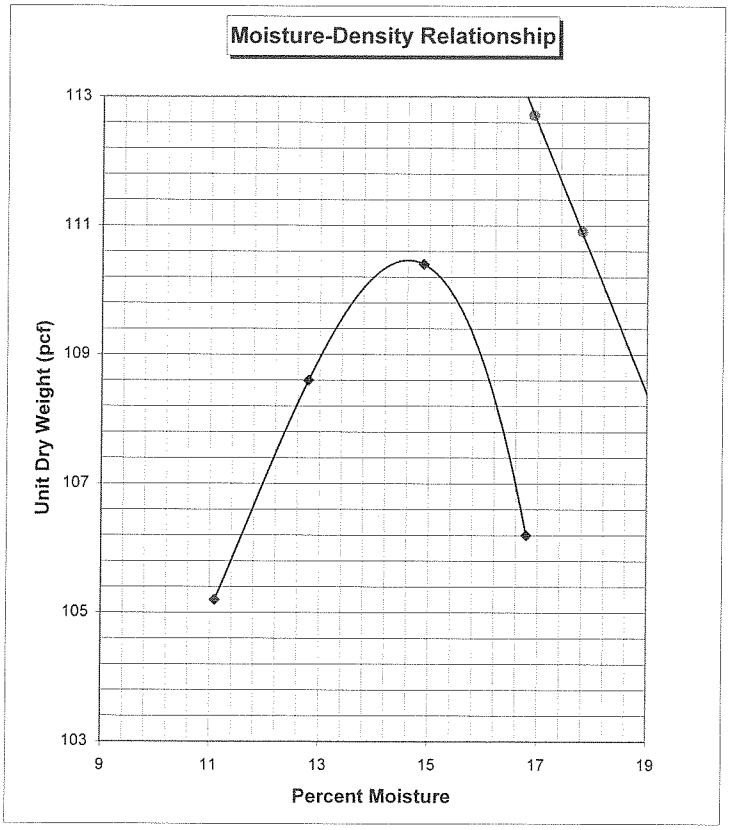

Compaction Test

Lab Compacted Samples (Finer Fraction)
Maximum Dry Unit Weight (pcf): 110.5
Optimum Moisture Content (%): 14.6

COPIES TO: 1-Above

Reviewed By: GM

Daren Potteiger

The results shown on this report are for the exclusive use of the client for whom they were obtained and apply only to the samples tested and/or inspected.
They are not intended to be indicative of the qualities of apparently identical products. The use of our name must receive our prior written approval. Reports must be reproduced in their entirety.